

Binary Mixture of Copper-Cobalt Ions Uptake by Zeolite using Neural Network

John Kabuba, Antoine Mulaba-Bafubiandi, Kim Battle

Abstract—In this study a neural network (NN) was proposed to predict the sorption of binary mixture of copper-cobalt ions into clinoptilolite as ion-exchanger. The configuration of the backpropagation neural network giving the smallest mean square error was three-layer NN with tangent sigmoid transfer function at hidden layer with 10 neurons, linear transfer function at output layer and Levenberg-Marquardt backpropagation training algorithm. Experiments have been carried out in the batch reactor to obtain equilibrium data of the individual sorption and the mixture of copper-cobalt ions. The obtained modeling results have shown that the used of neural network has better adjusted the equilibrium data of the binary system when compared with the conventional sorption isotherm models.

Keywords—Adsorption isotherm, binary system, neural network; sorption

I. INTRODUCTION

HEAVY metals are well known for toxicity and their disposal is a significant industrial waste problem. Their amount in the environment not only increases every year, but also they are not biodegradable and tend to accumulate in living organisms [1]. Treatment processes for the removal of heavy metals ions from wastewater include coagulation, carbon adsorption, ion exchange, precipitation, reverse osmosis, etc. [2]. The sorption processes are probably the most attractive among these methods, since their application is simple, and they require relatively mild operating conditions, although the cost of substrate materials and regeneration is the limiting factor [3]. For this reason it is important to look for low-cost sorbents that could replace synthetic ion exchange resins [4, 5].

J. Kabuba is with the Minerals Processing and Technology Research Center, School of Mining, Metallurgy and Chemical Engineering, Faculty of Engineering and The Built Environment, University of Johannesburg, PO BOX 526, Wits 2050, South Africa (phone: + 27-11-559-6724; fax: + 27-11-559-6430; e-mail: johnk@uj.ac.za).

A. Mulaba-Bafubiandi is with the Minerals Processing and Technology Research Center, School of Mining, Metallurgy and Chemical Engineering, Faculty of Engineering and The Built Environment, University of Johannesburg, PO BOX 526, Wits 2050, South Africa (phone: + 27-11-559-6215; fax: + 27-11-559-6194; e-mail: amulaba@uj.ac.za).

K. Battle is with the Faculty of Engineering and The Built Environment, University of Johannesburg, PO BOX 524 Auckland Park 2006, Johannesburg,, South Africa (phone: + 27-11-559-6002; fax: + 27-11-559-6430; e-mail: kbattle@uj.ac.za).

Natural zeolites are the most important inorganic cation exchangers that exhibit high ion exchange capacity, selectivity and compatibility with the natural environment [6]. They are naturally occurring alumina-silicate based minerals. Clinoptilolite is the most abundant natural zeolite that occurs in relatively large minable sedimentary deposits in sufficiently high purity in many parts of the world [7, 8]. For the effective utilization of a natural zeolite as an ion exchanger it is essential to have chemical models that help to describe accurately heavy metals exchange equilibria [1]. Originally, by analogy with the sorption process, empirical equations such as Freundlich or Langmuir were adjusted to experimental data. These approaches were successfully applied by Polzer et al. [9] to interpret transport of radionuclides in volcanic tuff media and by Zheng et al. [10] to explain transport of cesium ion in a hydrous sodium crystalline silicotitanate, labelled TAM-5. The present models proposed in the literature describe the process either as phase equilibrium, where deviation from the ideal adsorption behavior is explained in terms of energetic heterogeneity [11, 12], or in terms of the law of mass action. In the latter case, non-ideal behavior of the liquid and solid phase results from the interaction among counterions [13]. The thermodynamic model for ion exchange based on the Pitzer or Bromley equations used for calculation of the activity coefficients in liquid phase and the Wilson equation for the same in zeolite phase are excellent in prediction ion exchange equilibrium between aqueous solutions and clinoptilolite. However, sufficiently good results for binary systems are obtained assuming ideal behavior of the zeolite phase. The resulting average is lower than 8%. It should be emphasized that estimation of activity coefficients in the liquid phase is connected with the introduction into the equilibrium model two additional equations with two unknown Wilson's parameters, which significantly complicates the mathematical calculations. On the other hand, the calculated binary interaction parameters are very useful for estimation of equilibrium constants for multicomponent solutions. The target metal pollutants in this study were Cu (II) and Co (II) which is frequently found in industrial effluents. The modeling of binary adsorption equilibrium is still a challenging task. Several isotherms have been proposed to describe the equilibrium of such system but it was found that the mathematical description of sorption isotherms of the analyzed ions in the presence of one or two additional ions the solution is complicated from the theoretical point of view [14]. In this case the application of Neural Networks was proposed.

II. EXPERIMENTAL

A. Preparation of the adsorbent and synthetic solution

The clinoptilolite used in this study was sourced from the Vulture Creek, KwaZulu-Natal Province of South Africa [14]. The clinoptilolite was crushed and milled into powder with average particle sizes of approximately 75µm. The powder was then examined using an X-ray powder diffractometer (XRD) Phillips X'pert Model 0993 to determine its composition. Its elemental composition was determined using X-ray fluorescence spectroscopy (XRF, Phillips Magix Pro) while the surface area was analyzed using BET (Tristar 3000) [14]. The measurements were done under a nitrogen atmosphere. Prior to porosity and surface area analysis, 2g of sample was first degassed and nitrogen gas was flushed through for 4h at the solutions of Cu and Co were prepared by dissolving CuSO₄.5H₂O and CoSO₄.7H₂O respectively in deionizer water at pH 6.5. The synthetic wastewaters were prepared at five different Cu²⁺ and Co²⁺ ion concentrations, at 0.361, 1.099, 1.969 and 2.748 g/l. The solutions were assayed using atomic adsorption spectroscopy (AAS), (Model Varian Spectra (20/20)) [14].

B. Batch adsorption studies

The Cu and Co ion-exchange processes on the clinoptilolite were conducted at room temperature. Glass columns of 2cm diameter and 30cm of length were pre-loaded with 25g of either natural clinoptilolite (as received) or HCl-activated clinoptilolite [14]. Aliquots of 25 ml of the prepared Cu-bearing solutions of desired concentrations were passed through each of the two types of zeolites. These were afforded the same solution-zeolite contact time. After passing through the zeolite-packed column the resultant solutions were assayed using AAS in order to ascertain the zeolite's removal efficiency [14]. The flame type used was air-acetylene and the adsorption wavelengths for the metal were Cu (324.7nm). Standards of 1000 mg/l, 2000mg/l and 300mg/l were then prepared and a calibration curve was drawn using these standards. Dilution was applied stoichiometrically where the concentrations of the unknown solution of cobalt exceeded the standards' concentration range of the standards [14].

The percentage of ions removal as the output parameter of the NN model was considered as a measure of the uptake percentage. The uptake efficiency (%) was calculated as follows:

$$\% \text{ Uptake} = (C_0 - C_f) \times 100 / C_0 \quad (1)$$

Where C₀ and C_f are the initial and final ions concentrations of the solution, respectively

III. RESULTS AND DISCUSSION

A. Effect of pH

The metal ions removal was increased gradually with the increase in solution pH, as expected.

The variation in the removal of metal ion with respect to pH can be explained by considering the surface charge of the adsorbent material. The difference of the adsorption capacity of clinoptilolite for heavy metal ions may be due to a number of factors which include hydration diameter and solubility of cations. The hydrated radii of Cu (II) and Co (II) are 0.419 and 0.423 nm, respectively [15]. The Cu (II) particles should ideally be adsorbed in larger quantities compared to the Co (II) particles, since the smaller particles can pass through the micropores of the clinoptilolite structure with ease.

B. Effect of contact time and temperature

The effect of contact time on the adsorption of Cu (II) and Co (II) ions onto clinoptilolite was studied at various temperatures, i.e., 25, 35, 45 and 60. It was observed that the initial uptake rate for two metals was very high, as a large number of adsorption sites are available for adsorption at the onset of the process. It was established that at 25°C within the first hour of contact, almost 70% and 80% of Cu (II) and Co (II) ions, respectively, were adsorbed onto clinoptilolite. As the sites are gradually filled up, adsorption proceeds slower and the kinetics becomes more dependent on the rate at which the adsorptive is transported from the bulk phase to the actual adsorption sites. In the case of Co-Clino system, 2h was found to be sufficient to attain equilibrium at room temperature, whereas in the case of Cu-Clino system equilibrium was established within almost 1h. It was also found that the amount of adsorption decreases with increasing temperature in both systems.

Adsorption of metal ion on Clino adsorbent shows similar behaviour with respect to increase in temperature. The equilibrium adsorption capacity of Cu (II) and Co (II) ions onto Clino was favoured at lower temperatures. The decrease on the uptake of heavy metal ions with increase in temperature may be attributed to the increase in the average kinetic energy of the metal ions. The attractive forces between metal ions and Clino surface sites will become insufficient to retain the metal ion at the binding site of Clino. Therefore, increase in temperature may be associated with decrease in the stability of metal ion-adsorbent interaction.

C. Effects of initial metal ion concentration

The amount of metal ions adsorbed per unit mass (q_e) of Clino increases gradually with an increase in metal concentration, whereas the extent of radiation (%) decreases with increasing metal ion loading. At low concentration of the metal ions, a unit mass of the Clino is exposed to small number of metal ions and consequently the adsorption is independent of the initial metal ion concentration. The extent of adsorption comes down for a fixed adsorbent content at high metal ions concentration due to decreased number of available adsorption sites on Clino surface, Similar observations have been reported earlier on montmorillonite [17], Sawdust [18] and boron waste [19].

D. Single Component Isotherms

The mathematical expression that represents the Langmuir isotherm can be written as follows:

$$q_j^* = (q_m b_j C_j^*) / (1 + b_j C_j^*) \quad (2)$$

Where q_m and b_j are Langmuir isotherm constants. These constants have a physical meaning and b_j parameter represents the ratio between sorption and desorption rates. Therefore, the high b_j values indicate high affinity of the ion for the site of adsorbent material, while the q_m parameter represents the total number of available sites of the sorbent. When $b_j C_j^* > 1$, the isotherm is favourable, if $b_j C_j^* \ll 1$ the isotherm is quasi linear [20].

$$\text{The Freundlich isotherm: } q_j^* = a_j (C_j^*)^n \quad (3)$$

Where a_j and n are Freundlich isotherm constants.

The Freundlich isotherm does not predict the sorbent saturation. Thus, the model allows the existence of an infinite superficial covering. The Freundlich isotherm frequently is used to model the limited segments of experimental data [21].

The maximum adsorption capacity and affinity obtained for individual adsorption of Cu and Co ions by clino has presented the following order $\text{Cu} > \text{Co}$. Ma and Tobin [22] have justified this order of preference/affinity as a function of metallic ion chemical characteristics and to the bigger cobalt ionic radius, reducing its sorption in comparison with other ions.

E. Binary Component Isotherms

The multi-component Langmuir model was the most frequently used to fit the binary sorption data. The mathematical expression that represents the model of the Langmuir isotherm for a binary mixture can be written as follows:

$$q_1^* = (q_m b_1 C_1^*) / (1 + b_1 C_1^* + b_2 C_2^*) \quad (4)$$

Where q_m , b_1 and b_2 are the binary Langmuir isotherm constants.

Chong and Volesky [23] and Sanchez et al., [24] have applied a model originally developed by Bailey and Ollis [25] to represent the binary data of biosorption equilibrium.

The original model was developed to describe the non-competitive inhibition during enzymatic kinetic studies. This model is represented by (5):

$$q_1^* = (q_m b_1 C_1) [1 + (k/b_1) C_2^*] / (1 + b_1 C_1^* + b_2 C_2^* + 2k C_1^* C_2^*) \quad (5)$$

Where q_m , b_1 , b_2 and K are model constants.

Chong and Volesky [23] and Sanchez et al. [24] have been used modified models of the Langmuir isotherm to represent the biosorption equilibrium data in binary mixtures. These models have been developed through the incorporation of the new parameters to the original model of the Langmuir isotherm in (2).

Incorporating the new constants (k_1 , k_2) in the exponential form to the denominator of the Langmuir isotherm concentration, the following expression was achieved:

$$q_1^* = (q_m b_1 C_1^*) / [1 + b_1 (C_1^*)^{k_1} + b_2 (C_2^*)^{k_2}] \quad (6)$$

Adding the constants (k_1 , k_2) in the exponential form to the numerator and the denominator of the Langmuir isotherm concentration, the Langmuir-Freundlich isotherm [26] was obtained, which can be represented by the following mathematical expression:

$$q_1^* = (q_m b_1 C_1^*)^{k_1} / [1 + b_1 (C_1^*)^{k_1} + b_2 (C_2^*)^{k_2}] \quad (7)$$

Sag and Kutsal [27] have used the empirical Freundlich model to describe the biosorption equilibrium in binary systems, whose mathematical representation can be written as follows:

$$q_1^* = a_1 (C_1^*)^{n_1 + \alpha_{11}} / [(C_1^*)^{\alpha_{11}} + a_{12} (C_2^*)^{\alpha_{12}}] \quad (8)$$

$$q_2^* = a_2 (C_2^*)^{n_2 + \alpha_{22}} / [a_{21} (C_1^*)^{\alpha_{21}} + (C_2^*)^{\alpha_{22}}] \quad (9)$$

Where (a_1 , n_1) and (a_2 , n_2) are the Freundlich isotherm constants obtained from the individual components equilibrium data. The other constants are determined using the equilibrium binary data.

In the original Langmuir isotherm model, the chemical species 1 and 2 compete for the occupation of the same site in adsorbent. Jain and Snowyink [28] have proposed an adsorption model for the binary mixtures based on the hypothesis that a part of adsorption occurs without competition, where $q_{m1} \neq q_{m2}$. The model representation is given by the following equations:

$$q_1^* = \{[(q_{m1} - q_{m2}) b_1 C_1^*] / (1 + b_1 C_1^*)\} + \{q_{m2} b_1 C_1^* / (1 + b_1 C_1^* + b_2 C_2^*)\} \quad (10)$$

$$q_2^* = q_{m2} b_2 C_2^* / (1 + b_1 C_1^* + b_2 C_2^*) \quad (11)$$

The first term at the right-hand side of Eq. (10) is the expression of the Langmuir isotherm for the molecule number of chemical species 1 that adsorb without a competition and it is proportional to the numbers of sites ($q_{m1} - q_{m2}$). The second term represents the molecule number of chemical species 1 that adsorb on the sites q_{m2} with a competition based on the Langmuir adsorption model. The molecule number of species 2 that adsorb on the sites q_{m2} with the competition of species 1 can be calculated by (11).

Nomenclature

a_j Freundlich mono-component isotherm constant

b_j Langmuir isotherm constant ($m_{\text{equiv.}}/L$)

C_j concentration in the fluid phase ($m_{\text{equiv.}}/L$)

C_j^0 initial concentration in the fluid phase ($m_{\text{equiv.}}/L$)

k_1, k_2, k multi-component Langmuir-type constants

- n_j Freundlich mono-component isotherm constant
- m_s dry mass of zeolite (g)
- q_m Langmuir constant related to the capacity of adsorption ($m_{equiv./g}$)
- q^*_j concentration at equilibrium in the biosorbent ($m_{equiv./L}$)
- V solution volume (L)
- Subscripts "j" metal species.
- $\alpha_{12}, \alpha_{21}, \alpha_{11}, \alpha_{12}, \alpha_{21}, \alpha_{22}$ Freundlich binary isotherm constant

F. Modelling using the neural networks

In this study, Neural Network Toolbox was used to develop the NN model. A three-layer NN with tangent sigmoid transfer function (*tansig*) at hidden layer and a linear transfer function (*purelin*) at output layer was used. The data gathered from batch experiments was divided into input matrix and target matrix. The optimum architecture of the NN model and its parameters variation were determined based on the minimum value of the mean squared error of the training and prediction set. The training was stopped after 167 iterations for the Levenberg-Marquardt algorithm (LMA) because the differences between training and validation error started to increase. Fig. 1 illustrates training, validation and test mean squared errors for the LMA.

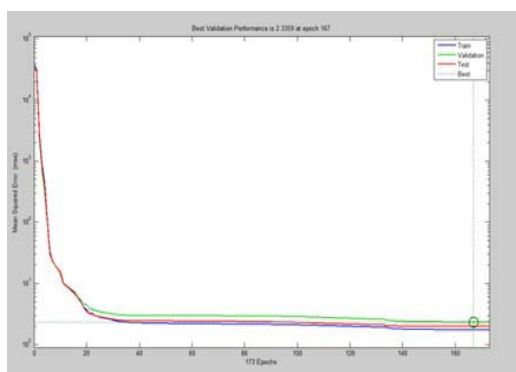


Fig. 1 Training, validation and test mean squared errors for the Levenberg-Marquardt algorithm.

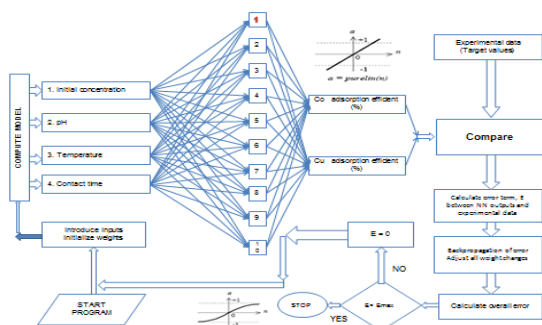


Fig. 2 The optimal architecture of NN

The optimal architecture of the NN model showed in Fig. 2 was determined based on minimum value of mean squared error of training and prediction set. The determination of neurons weights was carried out minimizing the objective function. The data sets were used to feed the optimized network in order to test and validate the model. Fig. 2 shows a comparison between predicted and experimental values of the output. For a search of the objective function minimum a simplex method was used originally developed by Nelder and Mead [15, 29]. This is a direct search method where only information about the objective function current values is used. To simulate the equilibrium data using NN, a data set including information about the equilibrium concentrations of each ion in the fluid phase like entrance net variables and ions adsorbed concentrations as exit net variables were used.

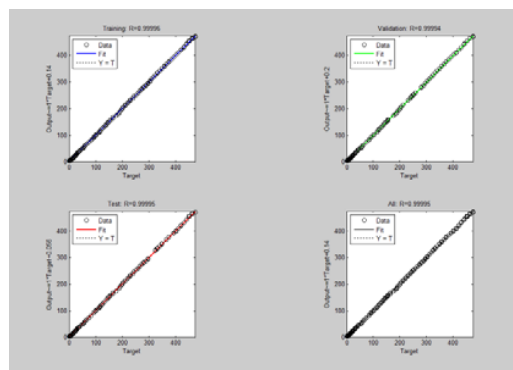


Fig. 3 Comparison between predicted and experimental values of the output

Different net structures with one hidden layer have been tested in a search of the best combination of connection weights to be achieved a smaller objective function values and average error. The absolute average deviation (AAD) and the objective function values for the architectures different types of the investigated net were used to represent the sorption equilibrium values of the Cu and Co binary system. The AAD was also proposed by Fagundes-Klen et al., [20] to simulate the equilibrium data of a binary stem Zn-Cd.

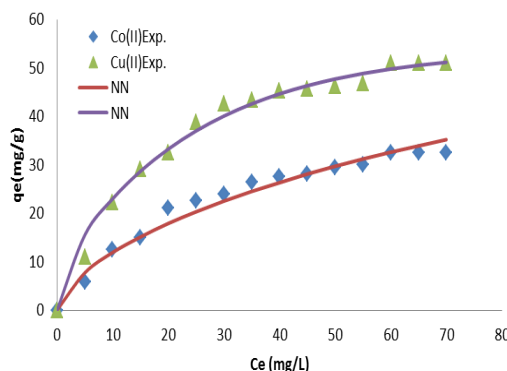


Fig. 4 Comparison of experimental and calculated data

Fig. 4 presents experimental versus calculated data for copper and cobalt. The modelling results of the equilibrium data of a binary system Cu-Co by using NN have better fitted experimental data compared to that one's obtained by using the adsorption isotherms [20].

IV. CONCLUSIONS

In this study, the adsorption equilibrium experimental data of the single-component system and the binary mixture of copper and cobalt ions were found to fit well using several isotherm models. However, it did not accurately predict the adsorption in a binary mixture. The NN technique was used to fit the experimental data and it was shown that this technique is more efficient comparing with the one using the adsorption isotherms models.

ACKNOWLEDGMENT

Research project is financed by UJ/ New Generation Scholarship.

REFERENCES

- [1] R Petrus, J Warchol. "Ion exchange equilibria between clinoptilolite and aqueous solution of $\text{Na}^+/\text{Ca}^{2+}$, $\text{Na}^+/\text{Cd}^{2+}$ and $\text{Na}^+/\text{Pb}^{2+}$ ". Microporous and Mesoporous Materials. vol. 61, 2003, pp.137-146.
- [2] W.W. Eckenfelder, Industrial Water Pollution Control, second ed., McGraw-Hill, New York, 1989.
- [3] S.C. Kesraoui-Ouki, R. Cheeseman, R.J. Perry. "Natural zeolite utilization in pollution control: A review of applications to metals' effluents". Chem. Technol. Biotechnol. vol.59, 1994, pp.121-126.
- [4] S.E. Bailey, T.J. Olin, R.M. Bricka, DD Adrian. "A review of potentially low-cost sorbents for heavy metals", Wat. Res. vol.33, 1999, pp. 2469-2479.
- [5] S.K. Ouki, M. Kavannagh. "Treatment of metal- contaminated wastewaters by use of natural zeolites". Wat. Sci. Tech. vol.39, 1999, pp.115-120.
- [6] F.A. Mumpton. "Natural zeolites: Occurrence, properties, use". Elmsford, New York, Pergamon Press. vol. 1676, pp. 309-318.
- [7] G. Gottardi, E. Gall. Natural Zeolites. Minerals and Rocks Springer-Verlag, 1985, p.321.
- [8] W.L. Polzer, M.G. Rao, H.R. Fuentes, R.J. Beckman. "Thermodynamically Derived Relationships between the Modified Langmuir Isotherm and Experimental Parameters," Environ. Sci. Technol., vol. 26- 9, 1992, pp.1780-1786.
- [9] Z. Zheng, D. Gu, R.G. Anthony. "Estimation of Cesium Ion Exchange when Using Crystalline Silico-titanates," Ind. Eng. Chem. Res., vol.34, 1995, pp. 2142-2147.
- [10] J. Novosad, A.L. Myers. "Thermodynamics of ion-exchange as an adsorption process". Can. J. Chem. Eng., vol.60, 1982, pp. 500-603.
- [11] S. Melis, G. Cao and M. Morbidelli, "A new model for the simulation of ion exchange. Equilibria", Ind. Eng. Chem. Res., vol.34, 1995, pp. 3916-3924.
- [12] F. Helfferich, Ion Exchange, McGraw-Hill, New York, 1962.
- [13] W. Kaminski, E. Tomczak, K. Jaros. "Interactions of metal ions sorbed on chitosan beads". Desalination. vol.218, 2008, pp. 281-286.
- [14] B.B. Mamba, D.W. Nyembe, A.F. Mulaba-Bafubiandi. "The effect of conditioning with NaCl, KCl and HCl on the performance of natural clinoptilolite's removal efficiency of Cu^{2+} and Co^{2+} from Co/Cu synthetic solutions". Water SA, vol.35, 2009, pp. 307-314.
- [15] T. Motsi, N.A. Rowson, M.J.H. Simmons. "Adsorption of Heavy Metals from Acid Mine Drainage by Natural Zeolite". Int. J. Miner.Process. vol. 92, 2008, pp. 42-48.
- [16] K.G. Bhattacharyya, S.S. Gupta. "Adsorption of a few heavy metals on natural and 5 modified kaolinite and montmorillonite: A review". Adv. Colloid Interface Sci. vol.140 6, 2008, pp. 114-131.
- [17] B Yu, Y Zhang, A. Shukla, SS Shukla, KL Dorris. "The removal of heavy metal from aqueous solutions by sawdust adsorption -removal of copper" J. Haz. Mat. vol.80, pp.33-42.
- [18] A. Olgun, N. Atar. "Removal of copper and cobalt from aqueous solution onto waste containing boron impurity". Chemical Engineering Journal. vol.167, 2011, pp. 140-147.
- [19] M.R. Fagundes-Klen, P. Ferri, T.D. Martins, C.R.G. Tavares, E.A. Silva. "Equilibrium study of the binary mixture of cadmium-zinc ions biosorption by the Sargassum filipendula species using adsorption isotherms models and neural network". Biochemical Engineering Journal. vol. 34. 2007, pp. 136-146.
- [20] B.E. Reed, M.R. Matsumoto. "Modeling Cadmium Adsorption by Activated Carbon Using the Langmuir and Freundlich Isotherm Expressions". Sep.Sci. Technol.vol. 28, 1993, pp.2179-2195.
- [21] W. Ma, J.M. Tobin. "Development of multimetal binding model and application to binary metal biosorption onto peat biomass". Water Res. vol.37, 2003, pp. 3967-3977.
- [22] K.H. Chang, B. Volesky. "Description of two metal biosorption equilibria by Langmuir-type models", Biotechnol. Bio. Eng. 47,1995 ,pp. 451-460.
- [23] A. Saez, A. Ballester, M.A. Blazquez, F. Gonzalez, J. Munoz, A. Hammami. "Biosorption of copper and zinc by Cymodocea no-dosa". FEMS Microbiol. Rev.vol. 23, 1999, pp.527-536.
- [24] J.E. Bailey, D.F. Ollis, Biochemical Engineering Fundamentals, 2nd ed., McGraw-Hill, New York, 1986.
- [25] D.M. Ruthven, Principles of adsorption and adsorption processes, John Wiley & Sons, New York, 1984.
- [26] Y. Sag, T. Kutsal. "The Simultaneous Biosorption of Cu (II) and Zn on Rhizopus arrhizus: Application of the Adsorption Models ". Hydrometallurgy. vol.50, 1998, pp. 297-314.
- [27] J.S. Jain, V.L. Snoeying. "Chromium removal by carbon adsorption". J Water, Poll. Control. Fed, 218, 2008, pp. 281-286.
- [28] J.T. Matheickal, Q. Yu, G.M. Woodburn. "Biosorption of cadmium (II) and copper (II) by pretreated biomass of marine alga Gracilaria fisheri". Water Res. vol.33, 1998, pp. 335-342.
- [29] J.T. Matheickal, Q. Yu. "Biosorption of lead (II) and copper (II) from aqueous solutions by pre-treated biomass of Australian marine algae". Bioresour. Technol. 69, 1999, pp. 223-229.
- [30] Q. Yu, P. Kaewsam, L.V. Duong. "Electron micro- scopy of biosorbents from marine macro alga. Durvillaea potatorum". Chemosphere vol.41, 2000, pp.589-594.
- [31] S.K. Jha, G. Madras. "Neural Network Modeling of Adsorption Equilibria of Mixtures in Supercritical Fluids". Ind. Eng. Chem.Res.44, 2005, pp. 7038-7041.
- [32] JA Nelder, R Mead, A simplex method for function minimization, comput. J.vol. 7, 1965, pp. 308-315.



John Kabuba is a Postgraduate student in the Department of Metallurgy, Faculty of Engineering and The Built Environment, University of Johannesburg. He holds a B.Eng. Degree and Master's Degree in Chemical Engineering. He is a recipient of several awards and scholarships for academic excellence. His research interests include Application of Neural Networks to engineering, Mineral processing and oil extraction. Kabuba has published more than 10 international peer reviewed papers in international scientific journals and conferences proceedings.



Antoine F. Mulaba-Bafubiandi is Professor, Head of School, School of Mining, Metallurgy and Chemical Engineering and Head: Mineral Processing and Technology Research Group, Department of Extraction Metallurgy, University of Johannesburg, South Africa. He holds a Ph.D.; M. Eng.; MSc; MBA. Technical areas of advice and applicable foundry/metal type: Bentonite, Coal dust, Foundry Raw materials, Foundry Waste Subject specialisations (relevant to training): Bentonite processing, clay processing, technology and science, Coal research and processing

Professional institute or industry association memberships: Fellow of the Southern African Institute of Mining and Metallurgy (SAIMM) Council member of SAIMM; International exposure/networks Belgium, Brazil, India; China, DRC Experience in the foundry industry 1 year at Technisch Universiteit Delft (Holland) using NDT on aluminium castings and weld Initiation and 6 months Supervision of bentonite activation project at TWR Follow up and examination of Master's degree work on green sand Have given i.e. facilitated short courses on "Defect in castings" Prof. A.F. Mulaba-Bafubiandi has an extensive experience on clays and clay minerals. He has initiated, conducted and supervised numerous clays related projects in the past 18 years.

Kimberly Battle is a Vice Dean: Teaching & Learning and Operations at the Faculty of Engineering and The Built Environment, University of Johannesburg, South Africa. She holds a PhD in Systems Engineering at the University of Pennsylvania, USA. Specialties: Large scale optimization and modeling, various analytical techniques (Neural Networks, Statistical techniques, just about any operations research techniques), world class manufacturing (i.e. Toyota Product System). Kim Battle has 4 years' experience in consultant-Industrial Engineering and operation research, 4 years' experience in Manufacturing Development Consultant and 7 years' experience in lecturing. Focus areas in Operations Research and Corporate Finance.