

Comparative Study of Static and Dynamic Bending Forces during 3-Roller Cone Frustum Bending Process

Mahesh K. Chudasama, Harit K. Raval

Abstract—3-roller conical bending process is widely used in the industries for manufacturing of conical sections and shells. It involves static as well as dynamic bending stages. Analytical models for prediction of bending force during static as well as dynamic bending stage are available in the literature. In this paper bending forces required for static bending stage and dynamic bending stages have been compared using the analytical models. It is concluded that force required for dynamic bending is very less as compared to the bending force required during the static bending stage.

Keywords—Analytical modeling, cone frustum, dynamic bending, static bending.

NOMENCLATURE

C	= strength coefficient for dynamic bending in N/mm^2
E	= Young's modulus (N/mm^2)
K	= strength coefficient for static bending (N/mm^2)
m	= strain rate sensitivity index
n	= strain hardening exponent
P	= Vertical load at the top roller and bending plate interface (N)
R	= radius of curvature of the bent plate (mm)
r_1	= radius of bottom roller (mm)
t	= thickness of the plate (mm)
U	= Vertical distance travelled by the top roller for first stage of static bending (mm)
x	= half the horizontal distance of the bottom roller centers (mm)
y	= distance of fiber from neutral plane (mm)
y_{ep}	= distance of the fiber upto which elasticity E is constant (mm)
β	= bottom roller inclination angle
γ	= Shear strain
ϵ	= strain
$\dot{\epsilon}$	= strain rate (m/s)
ζ	= stress ratio
θ	= Angle between frictional force and horizontal plane at the roller plate interface (radians)
μ	= coefficient of friction at roller plate interface
ν	= Poisson's ratio
σ_{yi}	= yield stress (N/mm^2)
τ	= Shear stress

1. INTRODUCTION

THE 3-roller bending is a continuous bending operation in which a metal sheet or plate is passed through sets of three rollers. Metal plate is kept between a top roller and two bottom rollers as shown in Fig. 1. The bending is achieved by lowering the top roller and then rotating the bottom rollers.

Dr. Mahesh K. Chudasama is Assistant Professor, Mechanical Engineering Department at Government Engineering College, Dahod (Gujarat) India – 389151 (e-mail: mckgecs@gmail.com).

Dr. Harit K. Raval is Professor, Mechanical Engineering Department at S. V. National Institute of Technology, Surat (Gujarat) India – 395007 (e-mail: hkraval1@yahoo.co.in).

The conical shells or sections widely used in process industries are manufactured by 3-roller bending machines. The mechanics of bending forces involved in the processing of conical sections or shells by 3-roller bending machines is complex and 3-dimensional force pattern is observed [1].

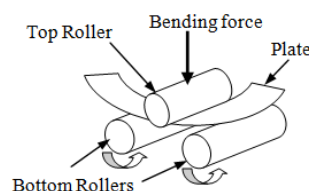


Fig. 1 Plate kept between Top and Bottom Rollers

Roll bending process is widely used process for producing cylindrical as well as conical sections and shells. Various researchers have analyzed the processes of roll bending. with the assumption of single pass bending analytical models for the moment and spring-back prediction for the roller bending of plates for cylindrical bending were developed [2]-[4]. Various researchers have developed analytical models of force or moment prediction for cylindrical bending [5]-[7]. Cone bending using compatible rollers have been investigated considering geometry using FEA methods [8]. Reaction force over the rollers using Finite Element Analysis has been reported and the results have been used to study the effects of temperature [9]. From the reviewed literature it is also found that work related to machine setting for required geometry and force for 3-roller bending has been reported [10]. 3-roller conical bending process for various cone geometries has been investigated considering the machine setting parameters [11], [12]. The 3-roller conical bending process is completed in of four stages: Static bending, forward rolling, backward rolling and unloading the plate from the rollers. The top roller of the 3-roller machine applies the force to bend the plate during the static bending stage. Analytical models for bending force prediction during static as well as dynamic bending stages have been reported [13]-[15]. The external bending moment required by the roller was equated with the internal bending moment developed in the plate to resist the bending to develop the analytical model of force predictions. Internal bending moment induced in the plate has been formulated assuming the simplified stress conditions. Based on the stress conditions, three cases can be assumed namely, 1. Major stress along an axis only, 2. Principal stress coinciding with the normal axis, and 3. Shear stresses along with the normal stresses. It is observed that case 3, i.e. considering shear stresses along with the normal stresses gives better

approximation of the bending force as compared to first two cases. Analytical models of bending force for static and

dynamic bending stages are reproduced as (1) and (2) respectively:

$$P_{static} = \frac{2 \int_0^{y_{ep}} \left[E'' \left(\frac{4}{3} \left(\frac{y}{R} \right)^2 + \gamma' \right) - \tau' \right]^{\frac{1}{2}} y dy + 2 \int_{y_{ep}}^{\frac{t}{2}} \left[K' \frac{2^{2n}}{\sqrt{3}} \left(\left(\frac{y}{R} \right)^2 + \gamma' \right)^n - \tau' \right]^{\frac{1}{2}} y dy}{\left(1 - \frac{x - r_1 \sin \theta}{a - r_1 \sin \theta} \right) \left(\frac{1}{\cos \theta + \mu \sin \theta} \right) [x - (r_1 - U) \tan \theta + \mu \{ x \tan \theta - r_1 (\sin \theta \tan \theta + \cos \theta - 1) - U \}]}$$
 (1)

$$\text{where } E'' = \frac{E'^2}{(1 + \zeta^2 - \zeta)}; \quad \gamma' = \gamma_{xy}^2 + \gamma_{yz}^2; \quad \tau' = \frac{3(\tau_{xy}^2 + \tau_{yz}^2)}{(1 + \zeta^2 - \zeta)}; \quad K' = \frac{K^2}{(1 + \zeta^2 - \zeta)}.$$

$$P_{dynamic} = \frac{\int_0^{y_{ep}} \left[\left(\frac{E' 2}{\sqrt{3}} \right)^2 \left(\left(\frac{y}{R} \right)^2 + \gamma_{xy}^2 + \gamma_{yz}^2 \right) - \frac{3(\tau_{xy}^2 + \tau_{yz}^2 + \tau_{yz}^2)}{(1 + \zeta^2 - \zeta)} \right]^{\frac{1}{2}} y dy + \int_{y_{ep}}^{\frac{t}{2}} \left[\left(\frac{C' 2^{2n}}{\sqrt{3}} \right)^2 \left(\left(\frac{y}{R} \right)^2 + \gamma_{xy}^2 + \gamma_{yz}^2 \right)^{\frac{1}{2}} - \frac{3(\tau_{xy}^2 + \tau_{yz}^2 + \tau_{yz}^2)}{(1 + \zeta^2 - \zeta)} \right]^{\frac{1}{2}} y dy}{\left[\left(\left(1 - \frac{x'}{a'} \right) \left(\frac{x - \tan \theta (r_1 - U)}{1 + \mu \tan \theta} \right) \right) - \left(\frac{\mu x'}{\cos \theta} \left(\sin \theta - \frac{x' \cos \theta}{U'} \right) \right) \right]}$$
 (2)

where, $x' = x - r_1 \sin \theta$; $a' = a - r_1 \sin \theta$; $U' = U - r_1 (1 - \cos \theta)$.

For comparison of static bending force and dynamic bending force, geometrical and material parameters (as per Table I), have been inserted in the analytical models of static and dynamic bending force. As the stress conditions considering case 3 are giving better approximation, analytical models considering case 3 for static as well dynamic bending are used for comparison. Analytical results of bending force for static and dynamic bending stage have been plotted on the same graph as shown in Fig. 2 considering different thicknesses and different bottom roller inclinations.

TABLE I
MATERIAL PROPERTY PARAMETERS TAKEN FOR ANALYTICAL CALCULATIONS

Plate Thickness, t (mm)	Yield Stress, σ_{yi} (N/mm ²)	Strength Coefficient, K (N/mm ²)	Strain Hardening Exponent, n
5.84	350	1219	0.30
7.88	278	817	0.24
8.86	320	897	0.25
11.84	346	916	0.23
13.96	270	913	0.24


For metal forming processes the range of the coefficient of friction is from 0.2 to 0.3. [16]. Hence the range of the values of friction coefficient ' μ ' is 0.2 to 0.3 is taken for the analytical calculation. Vertical Displacement of top roller 'U' for the first pass is 20 mm for plate thicknesses 5.84 mm, 7.87 mm and 8.85 mm, while 'U' is 15 mm and 10 mm for plate thicknesses of 11.84 mm and 13.97 mm respectively. Bottom roller radius ' r_1 ' is 80 mm and value of angle ' θ ' is calculated from the geometry of the setup and thickness of the plate. The value for strength coefficient ' C ' ranges from 1000 to 2000 N/mm² for structural steels [17]. Average value for the strength coefficient ' C ' as 1500 N/mm² is taken for dynamic bending force calculations. Similarly the value of strain rate ' $\dot{\epsilon}$ ' is taken to be 0.001 and the value of strain rate sensitivity index ' m ' is taken as 0.02 [17].

Dynamic bending force as percentage of static bending force has been calculated and tabulated as shown in Table II.


It can be observed from Fig. 2 and Table II that dynamic bending force required to bend the same thickness e.g. to bend 5.84 mm thickness plate is low. The similar results have been

reported by Gajjar et al. for cylindrical bending with 3-roller bending process [18]. Dynamic bending force is almost 10 to 20 % of the static bending force for the same thickness of the plate. Figs. 3 (a) and (b) show the bending phenomena occurring during static as well as dynamic bending. During static bending the whole plate length between the bottom rollers has to be bent by the bending force applied by the top roller. In case of dynamic bending, the bending line progresses through the plate length between bottom rollers and at instantaneous time the plate material near the bending line is to be bent and not the whole plate material between the bottom rollers as shown in Fig. 3 (b). The bending progresses through the plate length gradually and it will require less dynamic bending force as compared to static bending, wherein static bending the bending takes place throughout the material simultaneously and it will require higher bending force.


Again value of static bending forces is in the range of 10 to 20 times the dynamic bending forces because of the friction phenomenon. The friction at roller-plate interface opposes the bending force in case of static bending as shown in Fig. 4 (a) while the friction at roller-plate interface is in favor of the bending force in case of dynamic bending as shown in Fig. 4 (b). Hence, the bending force during static bending is quite higher as compared to the bending force required during the dynamic bending.

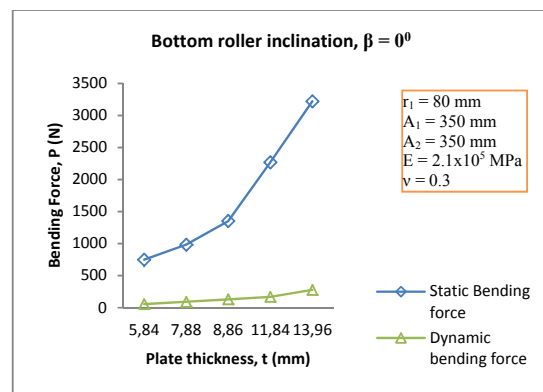


(a)

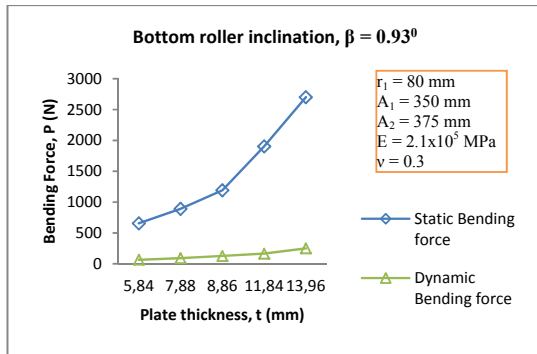


(b)

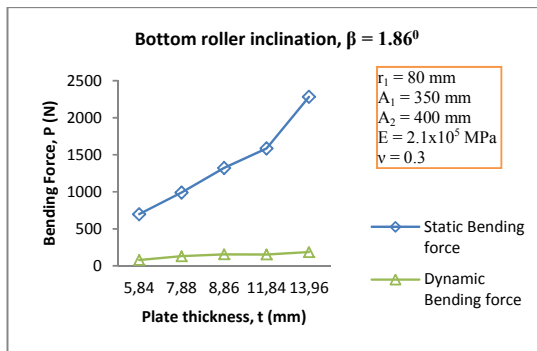

(c)

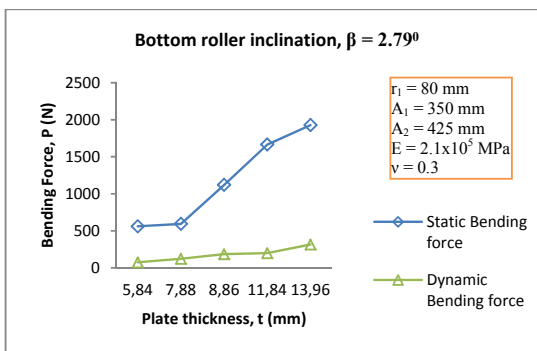


(d)

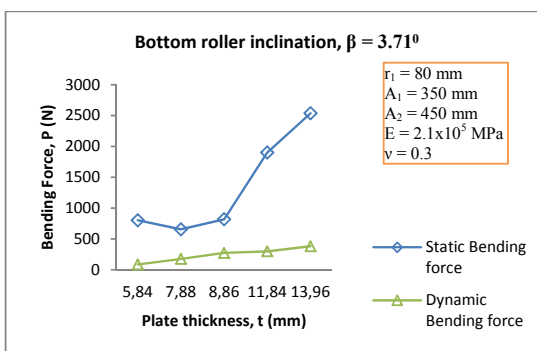

(e)

TABLE II
DYNAMIC BENDING FORCE AS PERCENTAGE OF STATIC BENDING FORCE FOR
DIFFERENT BOTTOM ROLLER INCLINATIONS CONSIDERING CASE-3

Thickness, t (mm)			
5.84			
Bottom Roller Inclination, β (degree)	Static Bending Force (N)	Dynamic Bending Force (N)	Dynamic Bending force as Percentage of Static bending force %
0.00	783.17	55.34	7.07
0.92	679.96	66.59	9.79
1.86	718.19	79.19	11.03
2.79	573.43	74.24	12.95
3.71	817.44	88.03	10.77
Thickness, t (mm)			
8.86			
Bottom Roller Inclination, β (degree)	Static Bending Force (N)	Dynamic Bending Force (N)	Dynamic Bending force as Percentage of Static bending force %
0.00	1351.46	129.71	9.60
0.92	1192.82	128.50	10.77
1.86	1321.84	155.86	11.79
2.79	1121.13	185.16	16.52
3.71	818.20	274.95	33.60
Thickness, t (mm)			
11.84			
Bottom Roller Inclination, β (degree)	Static Bending Force (N)	Dynamic Bending Force (N)	Dynamic Bending force as Percentage of Static bending force %
0.00	2270.57	168.90	7.44
0.92	1902.97	166.40	8.74
1.86	1585.64	153.22	9.66
2.79	1665.62	198.65	11.93
3.71	1901.46	299.79	15.77
thickness, t (mm)			
13.96			
Bottom Roller Inclination, β (degree)	Static Bending Force (N)	Dynamic Bending Force (N)	Dynamic Bending force as Percentage of Static bending force %
0.00	3224.41	276.65	8.58
0.92	2701.99	250.86	9.28
1.86	2282.15	186.83	8.19
2.79	1927.42	314.76	16.33
3.71	2537.30	382.69	15.08

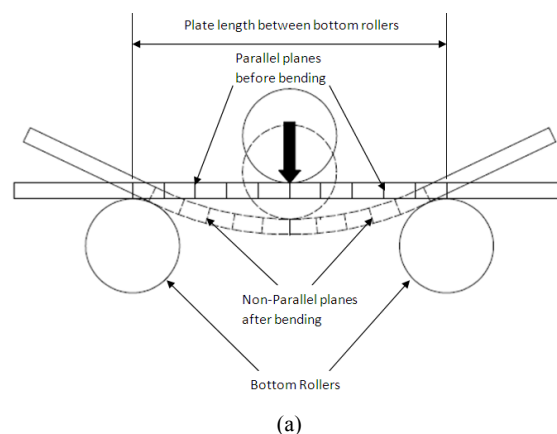

(a)

Fig. 2 Comparison of static and dynamic bending force

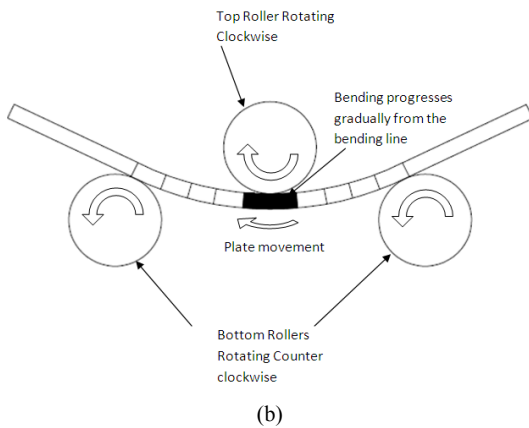


Fig. 3 (a) Bending phenomena during static bending (b) Bending phenomena during dynamic bending

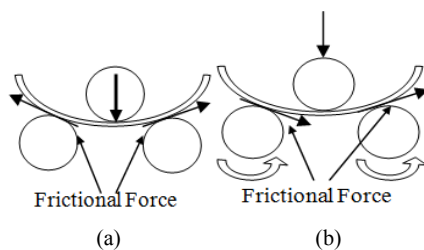


Fig. 4 (a) Frictional forces during static bending (b) Frictional forces during dynamic bending

It can also be observed from the Table II that as the bottom roller inclination increases dynamic bending force is relatively more with respect to static bending force, e.g. for 7.88mm thick plate and $\beta = 0$ the percentage of dynamic bending force is 9.33%, while for the same plate thickness and $\beta = 3.71$ it is 27.12%. It means that relatively higher dynamic bending force is required for higher bottom roller inclination for the constant plate thickness. It can be because of the shear stresses. During dynamic conditions shear stresses affects the dynamic bending force more as compared to affecting the static bending force.

It can also be observed from Table II that there is no set pattern of variation for either static bending force or dynamic bending force with respect to bottom roller inclination. In general it can be said from Table II that the static bending force decreases as the bottom roller inclination increases while the dynamic bending force increases as the bottom roller increases.

REFERENCES

- [1] MK Chudasama, HK Raval, 2013 "An approximate bending force prediction for 3-roller conical bending process", *International Journal of Material Forming*, Vol. 6 No 2 pp. 303-314.
- [2] M Hua, DH Sansome, K Baines, "Mathematical modeling of the internal bending moment at the top roll contact in multi-pass four-roll thin-plate bending", *Journal of Materials Processing Technology*, 1995, 52, 425-459.
- [3] K Baines, M Hua, IM Cole, KP Rao, "A formulation for determining the single-pass mechanics of continuous four-roll thin plate bending process", *J. Mater. Process. Techno.*, 67 1997 189-194.
- [4] M Hua, YH Lin, "Large deflection analysis of elastoplastic plate in steady continuous four-roll bending process", *International Journal of Mechanical Sciences*, 1999, 41, 1461-1483.
- [5] H Kim, N Nargundkar, T Altan, "Prediction of bend allowance and springback in air bending", *Trans. Of ASME, J. Mfg. Sci. Eng.*, 129 2007 342-251.
- [6] MB Basset, W Johnson, "The bending of plate using a three-roll pyramid type plate bending machine", *J. Strain Anal. Eng. Des.* 15 1966 398-414.
- [7] EA Kulikov, YI Berliner, GI Shevykov, "Bending thick walled conical vessel sections on roll bending machines", *Chem. Pet. Eng.* 5(12) 1969 977-979.
- [8] NE Hansen, O Jannerup, "Modelling of elastic-plastic bending of beams using a roller bending machine", *J. Eng. Ind.* 1013 1979 304-310.
- [9] Z Feng, H Champlaud, J Zeng, Thien-My Dao, "Investigation of influence of sliding of rolls over plate on continuous bending with non-compatible conical rolls", *Proceedings of 18th IASTED International Conference: Modelling and Simulation*, Montreal-Canada, 2007 527-531.
- [10] J Zeng, Z Liu, H Champlaud, "FEM dynamic simulation and analysis of the roll bending process for forming a conical tube", *J. Mater. Process. Techno.* 198 2008 330-343.
- [11] AH Gandhi, HK Raval, "Analytical and empirical modeling of top roller position for three-roller cylindrical bending of plates and its experimental verification", *J. Mater. Process. Techno.* 197 2008 268-278.
- [12] AH Gandhi, Investigation on machine setting parameters for 3-roller conical bending machine for springback, Ph. D. Thesis, 2009, S V National Institute of National Institute of Technology.
- [13] MK Chudasama, HK Raval, "Bending force prediction for dynamic roll-bending during 3-roller conical bending process", *Journal of Manufacturing Processes*, Vol. 16, 2014, pp. 284-295.
- [14] MK Chudasama, HK Raval, "Analytical model for prediction of force during 3-roller multipass conical bending and its experimental verification", *International Journal of Mechanical Engineering & Robotics Research*, Vol. 1, No.3, 2012, pp. 91-10.
- [15] MK Chudasama, HK Raval, "Development of analytical model for Dynamic bending force during 3-roller conical bending process", *Universal Journal of Mechanical Engineering*, Vol. 2, No. 4, 2014, pp. 148-154.
- [16] Z Marciniac, JL Duncan, SJ Hu, "Mechanics of sheet metal forming", 2nd Edition, Butterworth-Heinemann, 2002.
- [17] RL Brockenbrough, FS Merritt, "Structural steel designer's handbook", McGraw Hill Publishing, 2006.
- [18] HV Gajjar, AH Gandhi, TA Jafri, HK Raval, "Bendability Analysis for Bending of C-Mn Steel Plates on Heavy Duty 3-Roller Bending Machine", *International Journal of Mechanical, Industrial Science and Engineering*, 2007, 1(8), 19-24.