

# Analysis of Failure Pressures of Composite Cylinders with a Polymer Liner of Type IV CNG Vessels

A. Hocine, A. Ghouaoula, F. Kara Achira, and S.M. Medjdoub

**Abstract**—The present study deals with the analysis of the cylindrical part of a CNG storage vessel, combining a plastic liner and an over wrapped filament wound composite. Three kind of polymer are used in the present analysis: High density Polyethylene HDPE, Light low density Polyethylene LLDPE and finally blend of LLDPE/HDPE. The effect of the mechanical properties on the behavior of type IV vessel may be then investigated. In the present paper, the effect of the order of the circumferential winding on the stacking sequence may be then investigated. Based on mechanical considerations, the present model provides an exact solution for stresses and deformations on the cylindrical section of the vessel under thermo-mechanical static loading. The result show a good behavior of HDPE liner compared to the other plastic materials. The presence of circumferential winding angle in the stacking improves the rigidity of vessel by improving the burst pressure.

**Keywords**—CNG; Cylindrical vessel; Filament winding; Liner; Polymer; LLDPE; HDPE; Burst pressure.

## I. INTRODUCTION

THE CNG is considered as one of the more promising energy vectors of the future. It can be used as a fuel in many applications. However, this requires several technological hurdles to be cleared, especially the one concerning its storage. Storage must offer a high degree of safety as well as allowing ease of use in terms of energy density and dynamics of fuel storage and controlled release.

The use of composite materials is an extremely interesting alternative to metallic materials in the construction of vessels. Indeed, these materials are characterized by their lightness, rigidity, good fatigue strength, and corrosion resistance when their components are not metallic [1]. Thin or thick walled tanks are widely used in several branches of engineering, such as the storage of compressed hydrogen, liquefied and compressed natural gas [1].

A. Hocine is with the Mechanical Department – Faculty of Technology; Hassiba Benbouali University of Chlef BP .151, Chlef 02000, Algeria (phone: 00 213 27 72 17 94; fax: 00 213 27 72 17 94; e-mail: hocinea\_dz@yahoo.fr) .

A. Ghouaoula is with the Mechanical Department – Faculty of Technology; Hassiba Benbouali University of Chlef BP .151, Chlef 02000, Algeria (phone: 00 213 27 72 17 94; fax: 00 213 27 72 17 94; e-mail: ghouaoulamid@yahoo.fr).

F. Kara Achira is with the Mechanical Department – Sciences and Technology University Oran, Algeria (e-mail: karaachirafs@yahoo.fr).

S. D. Medjdoub is with the Mechanical Department – Faculty of Technology; Hassiba Benbouali University of Chlef BP .151, Chlef 02000, Algeria (phone: 00 213 27 72 17 94; fax: 00 213 27 72 17 94; e-mail: medjdoubssidimed@yahoo.fr).

Gas storage consists of keeping the gas at room temperature under pressure in a cylinder. The first tanks were type I, entirely of metal would be too heavy for storage of CNG. Storage cylinders for compressed natural gas (CNG) used in vehicles are pressure vessels that have been traditionally produced using isotropic materials, such as steel and aluminum [2].

A notable improvement of this first technology is to reinforce the cylinder by filament winding composite just on the cylindrical section (type II). Currently, two solutions have given good satisfaction tanks type III metallic liner - composite reinforcing and type IV tanks: plastic liner - composite reinforcement [3]. The polymer composites have recently been introduced for that purpose [2], usually relying on the composite manufacturing technique of filament winding (FW). The composite materials rolled on plastic liners offer several advantages, including: high strength, low thermal conductivity and a non-magnetic behavior [4-5-6]. And they can minimise the weight, improving the aesthetic and also increasing the pressure vessel mechanical, impact and corrosion behavior. The Compressed hydrogen storage at 350 - 700 bar in Type III (metal-lined) and Type IV (polymer lined) vessels has been demonstrated in a number of prototype fuel cell vehicles [7].

These are important attributes in many present and future industrial and non-industrial large scale applications, such as, for example, liquid filters and accumulators, hydrogen cell storage vessels, oxygen bottles, GNC, pipe transportation, etc [8].

Velosa and al has studied a new generation of composite pressure vessels, where the vessels consist on a thermoplastic liner wrapped with a filament winding glass fibre reinforced polymer HDPE liner [9]. A high density polyethylene (HDPE) was selected as liner and a thermosetting resin used as matrix in the glass and carbon reinforced filament wound laminate of hydrogen vessel storage subjected to localized fire [10].

Barboza and al. investigates the behavior under burst pressure testing of a pressure vessel liner, produced with a polymer blend of 95 wt.% low linear density polyethylene (LLDPE) and 5 wt.% of high density polyethylene (HDPE) [2].

Weon and al attempts to study how the thermal ageing has an effect on the mechanical and thermal behaviors and to gain fundamental understanding on the degradation mechanism of linear low density polyethylene (LLDPE) pipe. It is

expected that approaches for improving the durability and reliability of LLDPE pipe at operating conditions [11].

The present paper focalizes on the analysis of cylindrical vessels polymers reinforced by composite filaments under internal pressure with end effect. Three polymers are covered by this analysis, namely, LLDPE, HDPE and mixing LLDPE / HDPE. The effects of winding angle fiber composites and composite sequences on the burst pressure are the subject of this work.

## II. MATHEMATICAL FORMULATION

Considering a vessel storage type IV consisting of a polymer plastic liner and a multilayered composite made of a polymer resin reinforced with long fibers (see Fig. 1), the general stress-strain relationship for each k-th component submitted to an axisymmetric mechanical loading is given by [3]:

$$\begin{Bmatrix} \sigma_z \\ \sigma_\theta \\ \sigma_r \\ \tau_{\theta r} \\ \tau_{zr} \\ \tau_{z\theta} \end{Bmatrix}^{(k)} = \begin{bmatrix} C_{11} & C_{12} & C_{13} & 0 & 0 & C_{16} \\ C_{12} & C_{22} & C_{23} & 0 & 0 & C_{26} \\ C_{13} & C_{23} & C_{33} & 0 & 0 & C_{36} \\ 0 & 0 & 0 & C_{44} & C_{45} & 0 \\ 0 & 0 & 0 & C_{45} & C_{55} & 0 \\ C_{16} & C_{26} & C_{36} & 0 & 0 & C_{66} \end{bmatrix}^{(k)} \begin{Bmatrix} \varepsilon_z \\ \varepsilon_\theta \\ \varepsilon_r \\ \gamma_{\theta r} \\ \gamma_{zr} \\ \gamma_{z\theta} \end{Bmatrix}^{(k)} \quad (1)$$

Where  $z$ ,  $\theta$ ,  $r$  represent a cylindrical coordinate system.

In the particular case of an axisymmetric loading, the local balance equations becomes in each k-th component [3]:

$$\frac{d\sigma_r^{(k)}}{dr} + \frac{\sigma_r^{(k)} - \sigma_\theta^{(k)}}{r} = 0 \quad (2)$$

The radius  $r$  is such as  $r_0 \leq r \leq r_a$ , where  $r_0$  and  $r_a$  are the structure inner and outer radius respectively (see Fig. 2). The strain-displacement relationships are [3]:

$$\begin{cases} \varepsilon_r^{(k)} = \frac{dU_r^{(k)}}{dr}, & \varepsilon_\theta^{(k)} = \frac{U_r^{(k)}}{r}, & \varepsilon_z^{(k)} = \frac{dU_z^{(k)}}{dz} = \varepsilon_0 \\ \gamma_{z\theta}^{(k)} = \frac{dU_\theta^{(k)}}{dz} = \gamma_0 r, & \gamma_{zr}^{(k)} = 0, & \gamma_{\theta r}^{(k)} = \frac{dU_\theta^{(k)}}{dr} - \frac{U_\theta^{(k)}}{r} \end{cases} \quad (3)$$

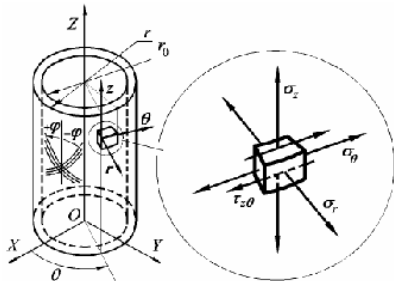


Fig. 1 Stress state in cylindrical part of type IV vessel [3]

The considered composite material is composed of an organic resin reinforced with long fibers. With respect to the local cylindrical co-ordinates system (see Fig. 3), the fourth order compliance tensor of composite  $S^c$  is reduced at the following form [3]:

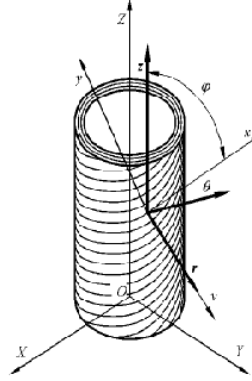


Fig. 2 Coordinate relation between cylindrical reference and the reference mark of the fiber [3]

$$S^c = \begin{bmatrix} S_{11}^c & S_{12}^c & S_{13}^c & 0 & 0 & 0 \\ S_{12}^c & S_{22}^c & S_{23}^c & 0 & 0 & 0 \\ S_{13}^c & S_{23}^c & S_{33}^c & 0 & 0 & 0 \\ 0 & 0 & 0 & S_{44}^c & S_{45}^c & 0 \\ 0 & 0 & 0 & S_{45}^c & S_{55}^c & 0 \\ 0 & 0 & 0 & 0 & 0 & S_{66}^c \end{bmatrix} \quad (4)$$

The damage seen in this work is related to the cracking of the resin along the direction of parallel fibers.

This type of cracking, assumed to change the compliance tensor components and to be more or less affected. In this context, three parameters of damage  $D_I$ ,  $D_{II}$  and  $D_{III}$  respectively are defined and they characterize the lower transverse modulus  $E_{22}$  and shear modulus  $G_{12}$  and  $G_{23}$  [12].

The damage will be introduced by adding the damage contribution tensor  $H$  to the compliance tensor of composite  $S^c$ . In the present analysis, there is only the difference in behavior between transverse stress and compression is taken into account.

The elements of the compliance tensor damage can be expressed in terms of the internal variable  $D_I$  and only the sign of the hoop stress [12].

$$\tilde{S}^c = S^c + H(S, D_I, \sigma_2) \quad (5)$$

Where, the damage contribution tensor  $H$  is given by:

$$H = \begin{bmatrix} 0 & 0 & 0 & 0 & 0 & 0 \\ 0 & H_{22} & h(\sigma_2) & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 & 0 & 0 \\ 0 & 0 & 0 & H_{44} & 0 & 0 \\ 0 & 0 & 0 & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 & 0 & H_{66} \end{bmatrix}$$

In this present analysis, considering the polymer liner as an anisotropic elastic material, the fourth order compliance tensor  $S_e^L$  is of the following form:

$$S_e^L = \begin{pmatrix} S_{11}^L & S_{12}^L & S_{13}^L & 0 & 0 & 0 \\ S_{21}^L & S_{22}^L & S_{23}^L & 0 & 0 & 0 \\ S_{31}^L & S_{32}^L & S_{33}^L & 0 & 0 & 0 \\ 0 & 0 & 0 & S_{44}^L & 0 & 0 \\ 0 & 0 & 0 & 0 & S_{55}^L & 0 \\ 0 & 0 & 0 & 0 & 0 & S_{66}^L \end{pmatrix}$$

Substituting the expression of radial and hoop stresses derived from equation (1) into equation (2) and using equation (3), the following differential equation is obtained [1-3]:

$$\frac{d^2 U_r^{(k)}}{dr^2} + \frac{1}{r} \frac{dU_r^{(k)}}{dr} - \frac{N_1^{(k)}}{r^2} U_r^{(k)} = [N_2^{(k)} \varepsilon_0 + N_3^{(k)} \Delta T] \frac{1}{r} + N_4^{(k)} \gamma_0 \quad (6)$$

Where

$$\begin{aligned} N_1^{(k)} &= \frac{C_{22}^{(k)}}{C_{33}^{(k)}} & N_2^{(k)} &= \frac{C_{12}^{(k)} - C_{13}^{(k)}}{C_{33}^{(k)}} & N_3^{(k)} &= \frac{K_3^{(k)} - K_2^{(k)}}{C_{33}^{(k)}} \\ N_4^{(k)} &= \frac{C_{26}^{(k)} - 2C_{36}^{(k)}}{C_{33}^{(k)}} & \alpha_2^{(k)} &= \frac{N_2^{(k)}}{1 - N_1^{(k)}} & \alpha_3^{(k)} &= \frac{N_3^{(k)}}{1 - N_1^{(k)}} \\ \alpha_4^{(k)} &= \frac{N_4^{(k)}}{4 - N_1^{(k)}} \end{aligned} \quad (7)$$

The solution of equation (16) depends on the value  $\beta^{(k)} = \sqrt{N_1^{(k)}}$ .

For  $\beta^{(k)} = 1$ :

$$U_r^{(k)} = D^{(k)} r + E^{(k)} / r + r \ln(r) \left( N_2^{(k)} \varepsilon_0 + N_3^{(k)} \Delta T \right) + \alpha_4^{(k)} \gamma_0 r^2 \quad (8)$$

For  $\beta^{(k)} = 2$ :

$$U_r^{(k)} = D^{(k)} r^{\beta^{(k)}} + E^{(k)} r^{-\beta^{(k)}} + \left( \alpha_2^{(k)} \varepsilon_0 + \alpha_3^{(k)} \Delta T \right) r + \frac{N_4^{(k)}}{2} \gamma_0 r^2 \ln(r) \quad (9)$$

For  $\beta^{(k)} \neq 1$  (or 2):

$$U_r^{(k)} = D^{(k)} r^{\beta^{(k)}} + E^{(k)} r^{-\beta^{(k)}} + \left( \alpha_2^{(k)} \varepsilon_0 + \alpha_3^{(k)} \Delta T \right) r + \alpha_4^{(k)} \gamma_0 r^2 \quad (10)$$

$D^{(k)}, E^{(k)}, \gamma_0$  and  $\varepsilon_0$  being integration constants. The superscript k is such as  $k \in [1, w]$ , where  $w = n_L + n_C + 1$ . The integration constants are calculated by using the boundary conditions, given by [1-3-12].

The type IV CNG storage tank is submitted to maximum 40 MPa internal pressure to keep the behavior of the liner purely elastic. The internal radius of the liner is 33 mm and its thickness is 2 mm. for this study, the thickness of each composite layer is 0.27 mm. the solutions are obtained by using the Matlab numerical code. Table I present the material properties of polymer plastic liner LLDPE, HDPE and LLDPE/HDPE and Table II present the properties of carbon/epoxy composite.

During this work, four types of stacking sequences reinforcing HDPE liners were analyzed (Table III).

TABLE I  
POLYMER PLASTIC LINER PROPERTIES

	Tensile Modulus [MPa]	Yield stress [MPa]
LLDPE [13]	64	10
HDPE[2]	1050	25
LLDPE/HDPE[2]	171.5	15

TABLE II  
ELASTIC PROPERTIES AND RUPTURE PARAMETERS [3]

	$E_x$ [GPa]	$E_y$ [GPa]	$G_{xy}$ [GPa]	$\nu_{yx}$
C/E	151	11	4	0,3

TABLE III  
STACKING SEQUENCES REINFORCING

Sequence	Type
Seq1	$[\pm\phi]_8$
Seq2	$[[+\phi]_7 + 90_2]$
Seq3	$[90_2 + [\pm\phi]_7]$
Seq4	$[90 + [\pm\phi]_7 + 90]$

### III. RESULTS AND DISCUSSION

The Fig. 3 show the variation the variation of TSAI HILL criterion according to the increasing of internal pressure for type the three polymer plastic liner reinforced by  $[\pm 60]_8$  sequence.

The yield stress is quickly achieved for the LLDPE polymer, to a pressure of 20 MPa, the blend LLDPE / HDPE has allowed to increase the pressure up to 30 MPa. For the HDPE polymer, the yield stress is reached only for a pressure of 40 MPa. This concluded that in the elastic domain, the polymer HDPE has best characteristics for storage and transport at high pressure. According to the using pressure

vessels, the choice of polymer can be made on the basis of the results obtained.

The results obtained show that increasing the pressure from 0 to 40 MPa did not affect the strength of the composite layers, where the results of the criterion TSAI HILL are still below 1 (Fig. 4).

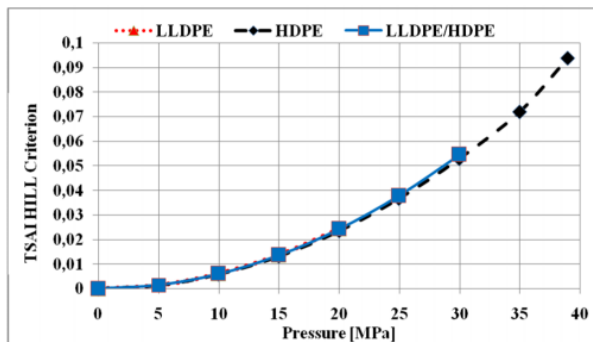


Fig. 3 Variation of Tsai Hill criterion with increasing internal pressure for first layered composite

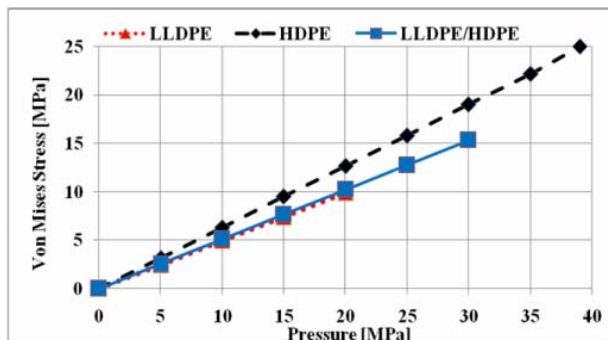


Fig. 4 Variation of Von Mises stress with increasing internal pressure for polymer liner

The effect of variation of the fiber orientation from 0 to 90° and stacking sequences of burst pressure is shown in Fig. 5. The figure shows clearly that the reinforcement of the composite layers by 90° circumferential winding has enabled increase the burst pressure tanks, mainly for winding angles of from 0 to 55°. The order of appearance 90° fibers also helped to improve the burst pressure, especially when it appears as first layer in the stacking sequence that will have a positive fact on the fracture behavior of pressure vessels.

#### IV. CONCLUSION

The focus to the analysis of the cylindrical part of a GNC storage vessel, combining a plastic liner and an over wrapped filament wound composite. Three kind of polymer are used in the present analysis: High density Polyethylene HDPE, Light low density Polyethylene LLDPE and finally blend of LLDPE/HDPE. The effect of the order of the circumferential winding on the stacking sequence has been investigated. The plastic liner is supposed to be an elastic material and for the composite is supposed to be an elastic –damageable material.

The results show the good behavior of HDPE, according to the other plastic materials tested in this analysis. The HDPE liner can resist to high pressure.

The reinforcement of stacking sequence by circumferential winding improves the rigidity of composite structure. The first appearance of 90° winding in stacking sequence, facts positively the burst pressure of cylindrical vessel.

In forthcoming paper, we also take into account, the elastoplastic behavior of HDPE liner, in order to improve the analytical model and to compare it with experimental test. An other hand, using commercial Finite Element Analysis (FEA) software is important in order to define adequate production parameters for the polymeric liner so that it could be successfully used in a composite pressure vessel.

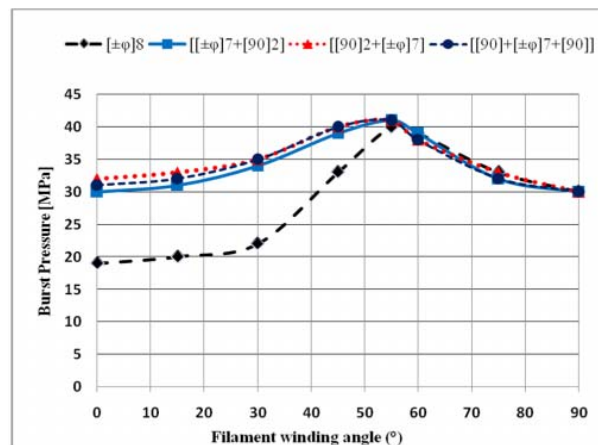


Fig. 5 Variation of burst pressure with increasing winding angle for different sequences

#### REFERENCES

- [1] Hocine A., Chapelle D., Boubakar L., Benamar A., Bezazi A.: Analysis of intermetallic swelling on the behavior of a hybrid solution for compressed hydrogen storage: Part I—Analytical modeling. *International Journal of Materials and design* 31 (2010) 2435-2443.
- [2] E.S. Barboza Neto, M. Chludzinski, P.B. Roesse, J.S.O. Fonseca, S.C. Amico, C.A. Ferreira. Experimental and numerical analysis of a LLDPE/HDPE liner for a composite pressure vessel - *Polymer Testing* 30 (2011) 693–700.
- [3] Hocine A., Chapelle D., Boubakar L., Benamar A., Bezazi A. Experimental and analytical investigation of the cylindrical part of a metallic vessel reinforced by filament winding while submitted to internal pressure. *International Journal of Pressure Vessels and Piping* 86 (2009) 649–655.
- [4] Lifshitz J.M., Dayan H. : Filament–wound pressure vessel with thick metal liner, *Composite Structures*, Vol 32, pp. 313-323, 1995.
- [5] Kabir M. Z. : Finite element analysis of composite pressure vessels with a load sharing metallic liner, *Composite Structures*, Vol. 49, pp. 247-255, 2000.
- [6] Vasiliev Vv., Krinakov A.A., Razin A.F. New generation of filament-wound composite pressure vessels for commercial applications, *Composite Structure*, Vol. 62, p. 449-459, 2003.
- [7] R.K. Ahluwalia, T.Q. Hua, J.K. Peng. On-board and Off-board performance of hydrogen storage options for light-duty vehicle. *International journal of hydrogen energy* 37 (2012) 2891-2910.
- [8] Brandt J, Drechsler K, Richter, H. The use of high-performance thermoplastic composites for structural aerospace applications. In: 9th international conference on composite materials (ICCM-9), vol. 6. Madrid, Spain; 1993. p. 143–150.

- [9] Velosa, J.P. Nunes, P.J. Antunes, J.F. Silva, A.T. Marques. Development of a new generation of filament wound composite pressure cylinders - J.C. - Composites Science and Technology 69 (2009) 1348–1353.
- [10] Jinyang Zheng, Kesheng Oua, Haiyan Bie, Ping Xu, Yongzhi Zhao, Xianxin Liu, Yuntang He. Heat transfer analysis of high-pressure hydrogen storage tanks subjected to localized fire. International journal of hydrogen energy 37 (2012) 13125 -13131
- [11] Jong-Il Weon. Effects of thermal ageing on mechanical and thermal behaviors of linear low density polyethylene pipe. Polymer Degradation and Stability. Volume 95, Issue 1, January 2010, Pages 14–20.
- [12] Ghouaoula A., Hocine A., Chapelle D., Kara Achira F., Boubakar M.L. Analytical damage prediction in the composite part of a type III hydrogen storage vessel. Mechanics of Composite Materials, Vol. 48, No. 1, March, 2012.
- [13] Ali Durmus,1 Ahmet Kas,Go` Z,1 And Christopher W. Macosko2. Mechanical Properties of Linear Low-density Polyethylene (LLDPE)/clay Nanocomposites. Journal of Macromolecular Sciencew,

**Abdelkader Hocine** was born in 1973, holds a degree in mechanical energy in 1996 from the Hassiba Benbouali University of Chlef. He underwent a 18-month doctoral studies in the laboratory of Applied Mechanics at Besancon France and he got his Ph.D. in June 2008. In April 2011, he obtained the degree of Associate Professor from University of Oran Algeria.

He teaches at the Department of Mechanical and he is interested in the mechanical behavior of composite tubular structures under various loading and supervises several areas of master and doctorate in this topic. Another axis of research has begun to take one space is the maintenance of industrial equipment.

He held the position of Chairman of the Scientific Council Faculty of Technology and LMD coordinator position at the university.

**Abdelhamid Ghouaoula** was born in 1983, holds a degree in mechanical energy in 2006 from the Saad Dahleb University of Blida. He holds a degree of Magister in 2011 from the Hassiba Benbouali University of Chlef. He enrolled in the first year PhD in 2012. He is interested in the mechanical behavior of composite tubular structures under various loading.

**Fouad Kara Achira** was born in 1972, holds a degree in mechanical energy in 1996 from the Saad Dahleb University of Blida. He holds a degree of Magister in 2003 from the Sciences and Technology University of Oran. He enrolled in the first year PhD in 2008. He is interested in the mechanical behavior of composite tubular structures under various loading. Actually he works on Petroleum Society.

**Sidi Mohamed Medjdoub** was born in 1976, holds a Magister degree in mechanical construction from the Sidi Bel Abbes University. He enrolled in the first year PhD in 2010. He teaches at the Department of Mechanical and he is interested in the mechanical behavior of composite tubular structures under various loading and supervises several areas of master in this topic.