

# Channel Length Modulation Effect on Monolayer Graphene Nanoribbon Field Effect Transistor

Mehdi Saeidmanesh, Razali Ismail

**Abstract**—Recently, Graphene Nanoribbon Field Effect Transistors (GNR FETs) attract a great deal of attention due to their better performance in comparison with conventional devices. In this paper, channel length Modulation (CLM) effect on the electrical characteristics of GNR FETs is analytically studied and modeled. To this end, the special distribution of the electric potential along the channel and current-voltage characteristic of the device is modeled. The obtained results of analytical model are compared to the experimental data of published works. As a result, it is observable that considering the effect of CLM, the current-voltage response of GNR FET is more realistic.

**Keywords**—Graphene nanoribbon, field effect transistors, short channel effects, channel length modulation.

## I. INTRODUCTION

GRAPHENE NANORIBBON (GNR) with remarkable electronic properties such as width-tunable energy band gap, high conductance and high carrier mobility, is known as a futuristic material to be used in next generation nanoelectronics devices [1]. It is observed that properties of GNR are similar to carbon nanotubes (CNTs), also GNR commonly has been created by unzipping multiwall carbon nanotubes (MWNTs) [2] as illustrated in Fig. 1.

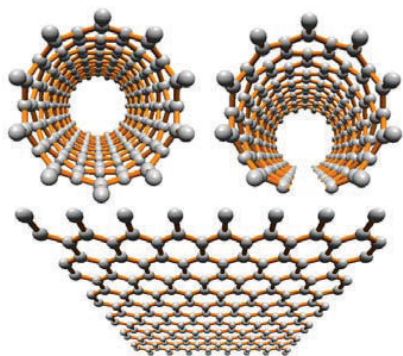


Fig. 1 The steps of unzipping the CNTs to form GNRs

Recently, the feasibility of using GNR as the channel material of FETs has been addressed [3]-[5]. A cross view of monolayer GNR FET with the definition of related geographic parameters is shown in Fig. 2. The major strength of adopting monolayer GNR as a channel material is due to its strong capability to control the electrostatics and hence expected to

reduce the short channel effects that rely on the device electrostatics [6]-[9].

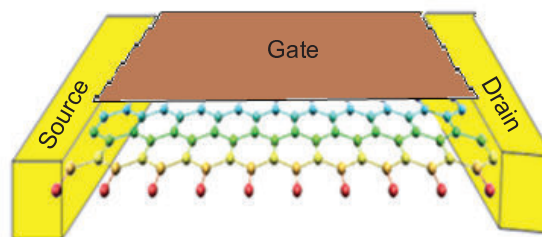


Fig. 2 A schematic of implemented FET with monolayer GNR as the channel material

Channel Length Modulation (CLM), which is defined as reduction of inverted channel region caused by large drain voltage is considered as one of the important short channel effects in FETs [10]. The output resistance decrement and current increment are two effects resulted by CLM in the FET which the latter is caused by the drain bias [10]. In this paper, an analytical model joint with numerical solution is proposed for CLM of monolayer GNR FET and its effects on drain current is studied. In Section II the proposed model for CLM is presented in detail, in Section III the simulated results are illustrated and discussed and finally Section IV concludes the study.

### A. Proposed Model

The inversion charge density at the drain terminal will be reduced as the drain voltage of FET rises. This decrement starts since the voltage along the oxide is decreasing and finally reaches to zero at  $V_{DS(sat)} = V_{GS} - V_T$  [10]. In addition, for drain-source voltages greater than saturation voltage, the inversion charge density is zero and the pinch-off point in the channel shifting from the drain to the source. In other words, depletion region extends laterally into the channel which makes the effective channel shorter than the physical gate length [11], [12]. This phenomenon is shown in Fig. 3. In addition, the effective channel length is assumed bias dependent and modulated by  $V_{DS}$ , since the width of depletion region is also bias dependent. In the presented model, the reduction of the effective channel is improved by employing a short-channel drain current model for GNR FET [13].

Mehdi Saeidmanesh is with the Computational Nanoelectronic Research Group (CoNE), Faculty of Electrical Engineering, Universiti Teknologi Malaysia, 81310 Skudai, Johor, Malaysia (e-mail: m.saeidmanesh@gmail.com).

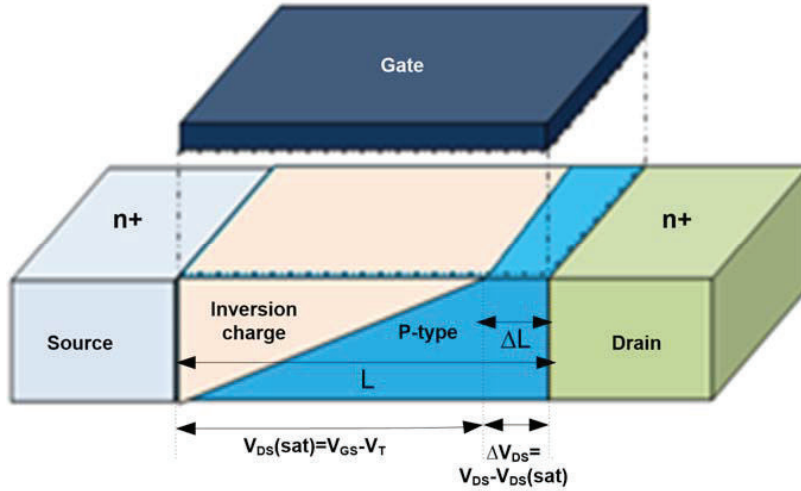


Fig. 3 The pinch-off phenomenon and shortening of the effective channel length resulted by high drain voltage

The derivative of the energy with respect to  $x$  is given by

$$\frac{dE}{dx} = \frac{N_d q + n_i q v L d t}{\epsilon} \quad (1)$$

where  $N_d$  is the donor impurity doping concentration,  $q$  is the electron charge magnitude,  $n_i$  is the intrinsic carrier concentration,  $v$  is the drift velocity,  $L$  is the channel length and  $\epsilon$  is the graphene permittivity constant. The second approximation is used to calculate the CLM and one dimensional (1D) Poisson equation is taken into account. The horizontal electric field,  $E_{sat}$ , is assumed to be at the pinch-off point for the inversion layer charge. Integrating over (1) specifies the electric field as

$$E(x) = \frac{N_d q x}{\epsilon} + \frac{n_i q x^2 L}{2\epsilon} + C_1 \quad (2)$$

where  $C_1$  is the integral constant. Applying the boundary conditions of  $E(x=0) = E_{sat}$ , the electric field in the space charge region considering CLM effect is given by

$$E(x) = \frac{N_d q x}{\epsilon} + \frac{n_i q x^2 L}{2\epsilon} + E_{sat} \quad (3)$$

The potential can be calculated by integrating over the electric field in the space charge region as

$$\varphi(x) = \frac{N_d q x^2}{2\epsilon} + \frac{n_i q x^3 L}{6\epsilon} + x E_{sat} + C_2 \quad (4)$$

where  $C_2$  is the integral constant. Based on the Fig. 3, the boundary condition  $\varphi(x=0) = V_{sat}$  can be used to obtain the constant  $C_2$ .

$$\varphi(x) = \frac{n_i q L}{6\epsilon} x^3 + \frac{N_d q}{2\epsilon} x^2 + E_{sat} x + V_{sat} \quad (5)$$

The space charge region width,  $\Delta L$ , reads

$$\left\{ \Delta L \rightarrow -\frac{b}{3a} - \frac{\left(\frac{1}{2\sqrt{3}}(-b^2+3ac)\right)}{\left(3aB^{\frac{1}{3}}\right)} + \frac{B^{\frac{1}{3}}}{32\sqrt{3}a} \right\} \quad (6)$$

where

$$B = \left( -2b^3 + 9abc + 27a^2vd - 27a^2vs + \sqrt{4(-b^2+3ac)^3 + (-2b^3+9abc+27a^2vd-27a^2vs)^2} \right)$$


In the proposed model of  $\Delta L$ , the two dimensional effects as well as the negative charges resulted by drain current are neglected. For  $x = \Delta L$ , the potential  $\varphi(x)$  will be equal to  $V_D$  which is given by

$$V_D = \frac{n_i q L}{6\epsilon} x^3 + \frac{N_d q}{2\epsilon} x^2 + E_{sat} x + V_{sat} \quad (7)$$

At the pinch of point, when the drain bias increases the effect of CLM which navigates a linear raise of the drain current, can be ignored by increasing threshold voltage [14]. The drain source current consists of diffusion and drift components. However, in the weak inversion where the device is on the subthreshold region, the diffusion part is the dominant part of drain-source current which is proportional to carrier concentration in this region [14]. The previous 2D potential model can be used to derive the subthreshold drain-source current [15], [16]. On the other hand, the off-state current which is defined by the current at zero gate-source voltage, is highly affected by the band gap in the monolayer GNR FET.

## II. RESULTS AND DISCUSSION

According to the relationship between the potential and drain current, the current-voltage characteristics of the modeled monolayer GNR FET is depicted in Fig. 4. It can be seen that as  $V_{DS}$  increases, the  $I_{DS}$  increases and there is a linear relation between them for small values of  $V_{DS}$ , while  $I_{DS}$  saturated for high values of  $V_{DS}$ .


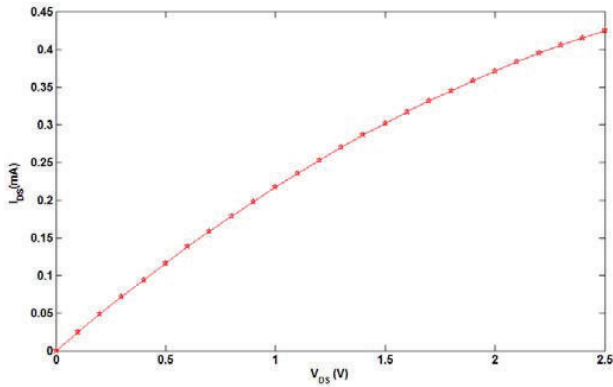
Fig. 4  $I_{DS}$  -  $V_{DS}$  characteristic of monolayer GNR FET

As the channel length and drain current have a reverse relation, one can write

$$I'_D = \left(\frac{L}{L-\Delta L}\right)I_D \quad (8)$$

The I-V characteristic of monolayer GNR FET for different values of  $V_{gs}$  is plotted in Fig. 5. It can be seen that as  $V_{gs}$  increases the  $I_{DS}$  also increases, in addition the effect of CLM is taken into account.

Fig. 6 indicates comparison between the current-voltage characteristic of analytical GNR FET model and experimental data. According to Figs. 5 and 6, the  $I_{DS}$  -  $V_{DS}$  characteristic of analytical model considering channel length modulation effect is nearer to experimental data.

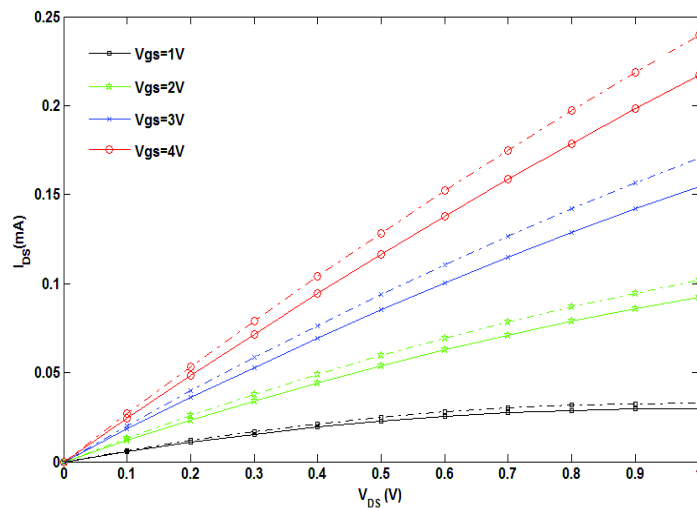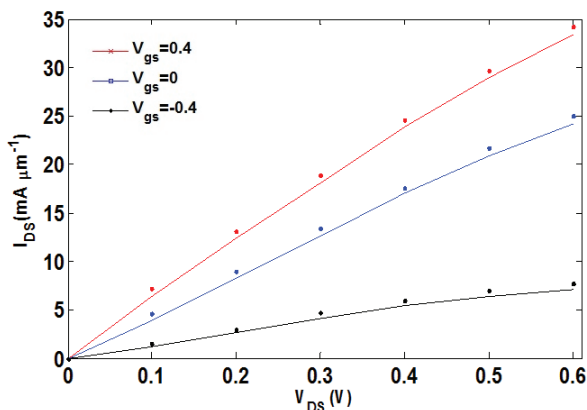Fig. 5 Current-Voltage characteristic of GNR FET for different values of  $V_{gs}$  with (dashed lines) and without (solid lines) channel length modulation effectFig. 6 Comparison between the  $I_{DS}$  -  $V_{DS}$  characteristic of analytical model considering channel length modulation effect (solid lines) and experimental data extracted from [ ] (symbols).

### III. CONCLUSION

In this paper, the effect of channel length modulation on monolayer GNR FETs is analytically studied. To this end, a model is developed for current-voltage, and the obtained results of analytical model are compared against the experimental data of published works. Accordingly, the comparison between analytical results of the model and experimental data indicates that taking into account CLM effect is more accurate to study the behavior of GNR FETs.

### ACKNOWLEDGEMENT

The authors are thankful to UTM UNIVERSITY GRANT PROGRAM (GUP, Tier1), and Project No: Q.J130000.7123.02H24, with title "Graphene Nano ribbon and Scrolls Super capacitor Modeling".

### REFERENCES

- [1] Xu, G.Y., et al., *Edge Effect on Resistance Scaling Rules in Graphene Nanostructures*. Nano Letters, 2011. 11(3): p. 1082-1086.
- [2] Xie, Y.E., Y.P. Chen, and J.X. Zhong, *Electron transport of folded graphene nanoribbons*. Journal of Applied Physics, 2009. 106(10).

- [3] B. N. Szafranek, D. Schall, M. Otto, D. Neumaier, H. Kurz, High on/off ratios in bilayer graphene field effect transistors realized by surface dopants, *Nano Letters* 11 (7) (2011) 2640–2643.
- [4] P. Wessely, F. Wessely, E. Birinci, U. Schwalke, B. Riedinger, On/offcurrent ratios of transfer-free bilayer graphene fet's as a function of temperature, in: *Design Technology of Integrated Systems in Nanoscale Era (DTIS), 2012 7th International Conference on, 2012*, pp. 1–3.
- [5] Thornhill, S., et al., *Graphene nanoribbon field-effect transistors*. Proceedings of 2008 Ieee International Symposium on Circuits and Systems, Vols 1-10, 2008: p. 169-172.
- [6] Li, J., et al., *Study on two-dimensional analytical models for symmetrical gate stack dual gate strained silicon MOSFETs*. Chinese Physics B, 2010. 19(10).
- [7] R. Sako, H. Tsuchiya, M. Ogawa, Influence of band-gap opening on ballistic electron transport in bilayer graphene and graphene nanoribbon FETs, *Electron Devices, IEEE Transactions on* 58 (10) (2011) 3300 – 3306.
- [8] M. Cheli, G. Fiori, G. Iannaccone, A semianalytical model of bilayergraphene field-effect transistor, *Electron Devices, IEEE Transactions on* 56 (12) (2009) 2979 –2986.
- [9] E. Sano, T. Otsuji, Bandgap Engineering of Bilayer Graphene for Field-Effect Transistor Channels 48 (2009) 14–16.
- [10] Neamen DA: *Semiconductor Physics and Devices*. 3rd edition. New York: McGraw Hill;2003.
- [11] Cousin, B., et al., *A unified short-channel compact model for cylindrical surrounding-gate MOSFET*. *Solid-State Electronics*, 2011. 56(1): p. 40-46.
- [12] Weidemann, M., et al., *2D Physics-based Compact Model for Channel Length Modulation in Lightly Doped DG FETs*. *Mixdes 2009: Proceedings of the 16th International Conference Mixed Design of Integrated Circuits and Systems, 2009*: p. 387-391.
- [13] Hariharan, V., et al., *Drain current model for nanoscale double-gate MOSFETs*. *Solid-State Electronics*, 2009. 53(9): p. 1001-1008.
- [14] Wie, C.R., *Nonsaturating Drain Current Characteristic in Short-Channel Amorphous-Silicon Thin-Film Transistors*. *Ieee Transactions on Electron Devices*, 2010. 57(4): p. 846-854.
- [15] Alam, K., *Transport and performance of a zero-Schottky barrier and doped contacts graphene nanoribbon transistors*. *Semiconductor Science and Technology*, 2009. 24(1).
- [16] Ryzhii, V., et al., *Current-voltage characteristics of a graphene-nanoribbon field-effect transistor*. *Journal of Applied Physics*, 2008. 103(9).